

AN EXPERIMENTAL STUDY ON REINFORCED CONCRETE CIRCULAR COLUMNS HEAVILY CONFINED BY SPIRAL REINFORCEMENT

J. CAI

K. SUZUKI

Department of Civil Engineering
South China University of Technology
Wusan, Guangzhou 510641, P. R. China

Department of Architectural Engineering
Osaka University
2-1 Yamadaoka, Suita, 565 Osaka, Japan

ABSTRACT

An experimental study was conducted to investigate the behavior of reinforced high strength concrete circular columns heavily confined by spiral reinforcement, which were subjected to high intensity reversed cyclic lateral load and constant high axial load. In this paper, the experimental work and a part of experimental results are described and discussed, which include the failure process, the lateral deflection characteristics, the axial displacement characteristics, the ultimate moment and the ultimate deflection capacity.

KEYWORDS

Reinforced concrete; circular columns; cyclic load; spiral reinforcement; properties; high strength.

INTRODUCTION

The design of columns at the lower-story of high-rise building is very important, because the columns are subjected to high axial load, which results in the deterioration of ductility of columns. Generally, using high strength concrete is a way to reduce the axial load ratio of the columns and to cut down the section size of the columns, however, higher strength concrete shows more brittle behavior, which necessarily leads to deterioration of ductility of the columns. The ductility of reinforced concrete columns is important in evaluating their aseismicity behavior, because the column with excellent ductile behavior should be capable of absorbing and dissipating seismic energy. Reinforced concrete circular columns show almost the same behavior in every direction, and the ductility behavior of the columns can be markedly improved by providing the circular spiral reinforcement to confine the concrete in compressive zone, which has been proved by author's former experimental study (Suzuki *et al.*, 1985) and practical earthquake damage. It can be regarded as reasonable to apply this column form in lower-story columns of high-rise building.

The object of this study is to investigate the basic mechanical properties of reinforced high-strength concrete circular columns with heavily confined by circular spiral reinforcement, which are subjected to scores of high intensity reversed cyclic lateral load and constant axial load.

EXPERIMENT

Figure 1 shows a typical test specimen, its dimension and bar arrangement. Details of column sections and

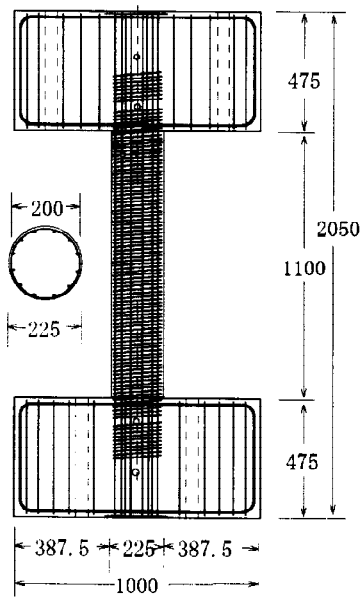


Fig. 1. Typical test specimen

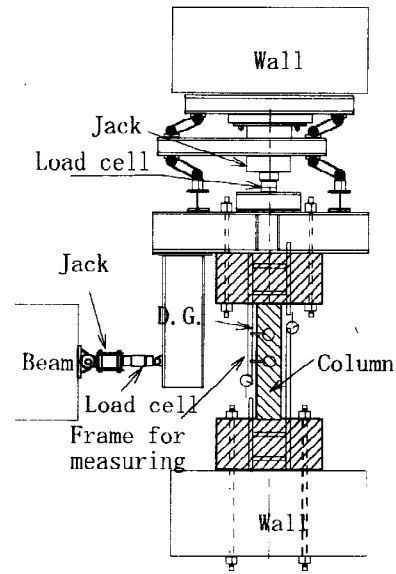


Fig. 2. Loading and measuring arrangement

strength of material used are given in Table 1. All specimens were designed to have higher beam strength capacity than that of column and have higher shear capacity than that of flexural capacity of column to assure that the flexural failure only occurred in the column. The main variables, as shown in Table 1, were the amount and the yield strength of circular spiral reinforcement, the axial load ratio and the strength of concrete.

Loading and measuring arrangement is shown in Figure 2. Reversed lateral load was applied alternately by a 1000 kN hydraulic jack through a "L" form rigid frame. The axial load was kept constant by adjusting the axial loading hydraulic jack (2000 kN capacity). The tests were carried out by deflection controlled method, and consisted of 5 cycles for each planned relative rotation angles of column (θ) such as 1/100, 1/50, 1/30, 1/20 and 1/15. In order to investigate the behavior of specimen No.6, which was extremely heavily confined, the loading cycles was increased to 30 at $\theta=1/15$.

Table 1. Details of column sections and mechanical properties of material

Specimen	f_c	N	$N/(Af_c)$	Spiral reinforcement			Main rein. f_y (MPa)
	(MPa)		η	Pitch	p_v (%)	f_{sv} (MPa)	
No.1	50.5	960	0.48	D6@25	2.56	385	357
No.2	49.5	1225	0.62	D6@25	2.56	385	357
No.3	55.8	686	0.31	D6@25	2.56	385	357
No.4	58.8	1460	0.62	D6@25	2.56	921	357
No.5	51.5	1245	0.61	D6@15	4.26	385	357
No.6	60.1	1431	0.60	D6@6.4	10.0	385	357
No.7	31.1	1245	1.01	D6@15	4.26	385	357


Lateral deflections and axial compressive displacement of columns were measured by displacement transducers attached to the measuring small light-steel rigid frame. The strain distribution of longitudinal and spiral reinforcement of columns were measured by electrical resistance strain gages.

FAILURE CHARACTERISTICS OF COLUMNS


Since columns were heavily confined by enough spiral reinforcement, the shear capacity of columns was fully

assured. All specimens show a failure mode of both column ends due to combined bend and compression. The failure process of column is as follows.

In the initial loading with $\theta = 1/100$, the outmost compressive longitudinal bars yield, cover concrete fractures and flexural crack appears. With the development of cover concrete fracture, cover concrete begins to scale off in tiny pieces, outmost tensile longitudinal bars yield. In large deformation cyclic loading with $\theta \geq 1/50$, the development of cover concrete fracture and scaling is fast, spiral reinforcement yields, column reaches the ultimate moment capacity and core concrete begins to fracture and scale off as well. The failure of specimen was due to the rupture of spiral reinforcement or, the buckling of compressive longitudinal bars, or severe fracture and scaling of core concrete under cyclic load. The failure development of specimens is relatively fast for those subjected to high axial load, with relatively small amount of spiral reinforcement. Figure 3 are two examples of visual damage of specimen.

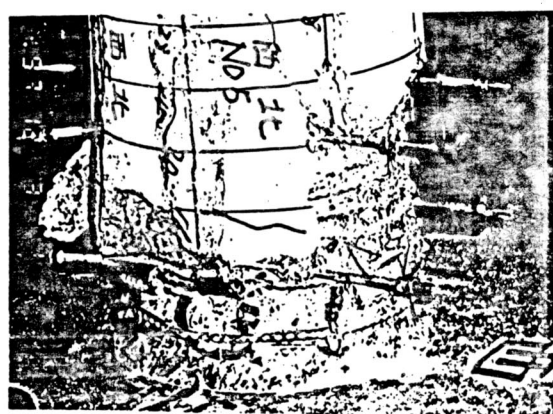

(a) Specimen No.5

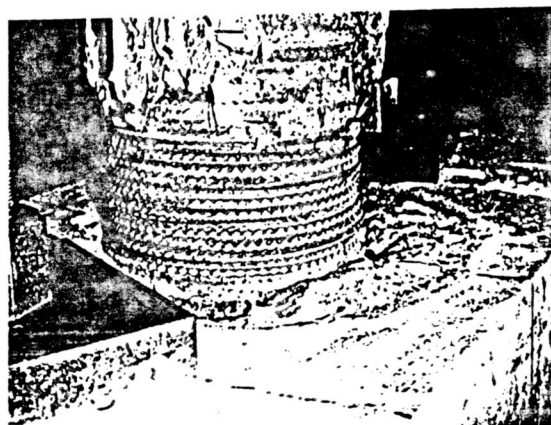

(b) Specimen No.6

Fig. 3. Examples of visual damage of specimen

LATERAL LOAD-DEFLECTION LOOPS

Figure 4 shows relations of the lateral load (V)-deflection (δ_h) of columns obtained from the experiment. The characteristics of these curves are discussed as follows.

Specimens No.1~No.3 are three specimens subjected to different axial load ratio only. With the increase of axial load ratio, the drop of the column load capacity increases due to cyclic load effect, and the column deflection capacity decreases. It also can be seen that from the V - δ_h curves corresponding to each loading datum displacement, the curve of specimen with small axial load ratio has a inverted "S" shape, dissipating less energy, while the specimen with larger axial load ratio has a shuttle shape, dissipating larger energy.

Compared with specimen No.2, specimen No.5 and No.6 have closer spiral reinforcement spacing, and No.4 uses higher strength spiral reinforcement. From the V - δ_h curves of these specimens, it can be seen that spacing and strength of spiral reinforcement have little effect on curves in the deformation range $\theta \leq 1/100$, but have destine effect on curves in the larger deformation range. With decrease of spiral reinforcement spacing or promotion of its strength, the deterioration of load capacity of specimen decreases and deflection capacity increases, because the core compressive concrete is more effectively confined. In details, for specimen No.2, it failure under cyclic load at $\theta = 1/30$, for specimen No.6 which has minimum spacing of spiral reinforcement, although it had experienced 5 cycles of loading at every loading datum rotation angle before $\theta = 1/15$ respectively, it could bore 30 cycles of loading at $\theta = 1/15$. Figure 5 shows the reduction ratio

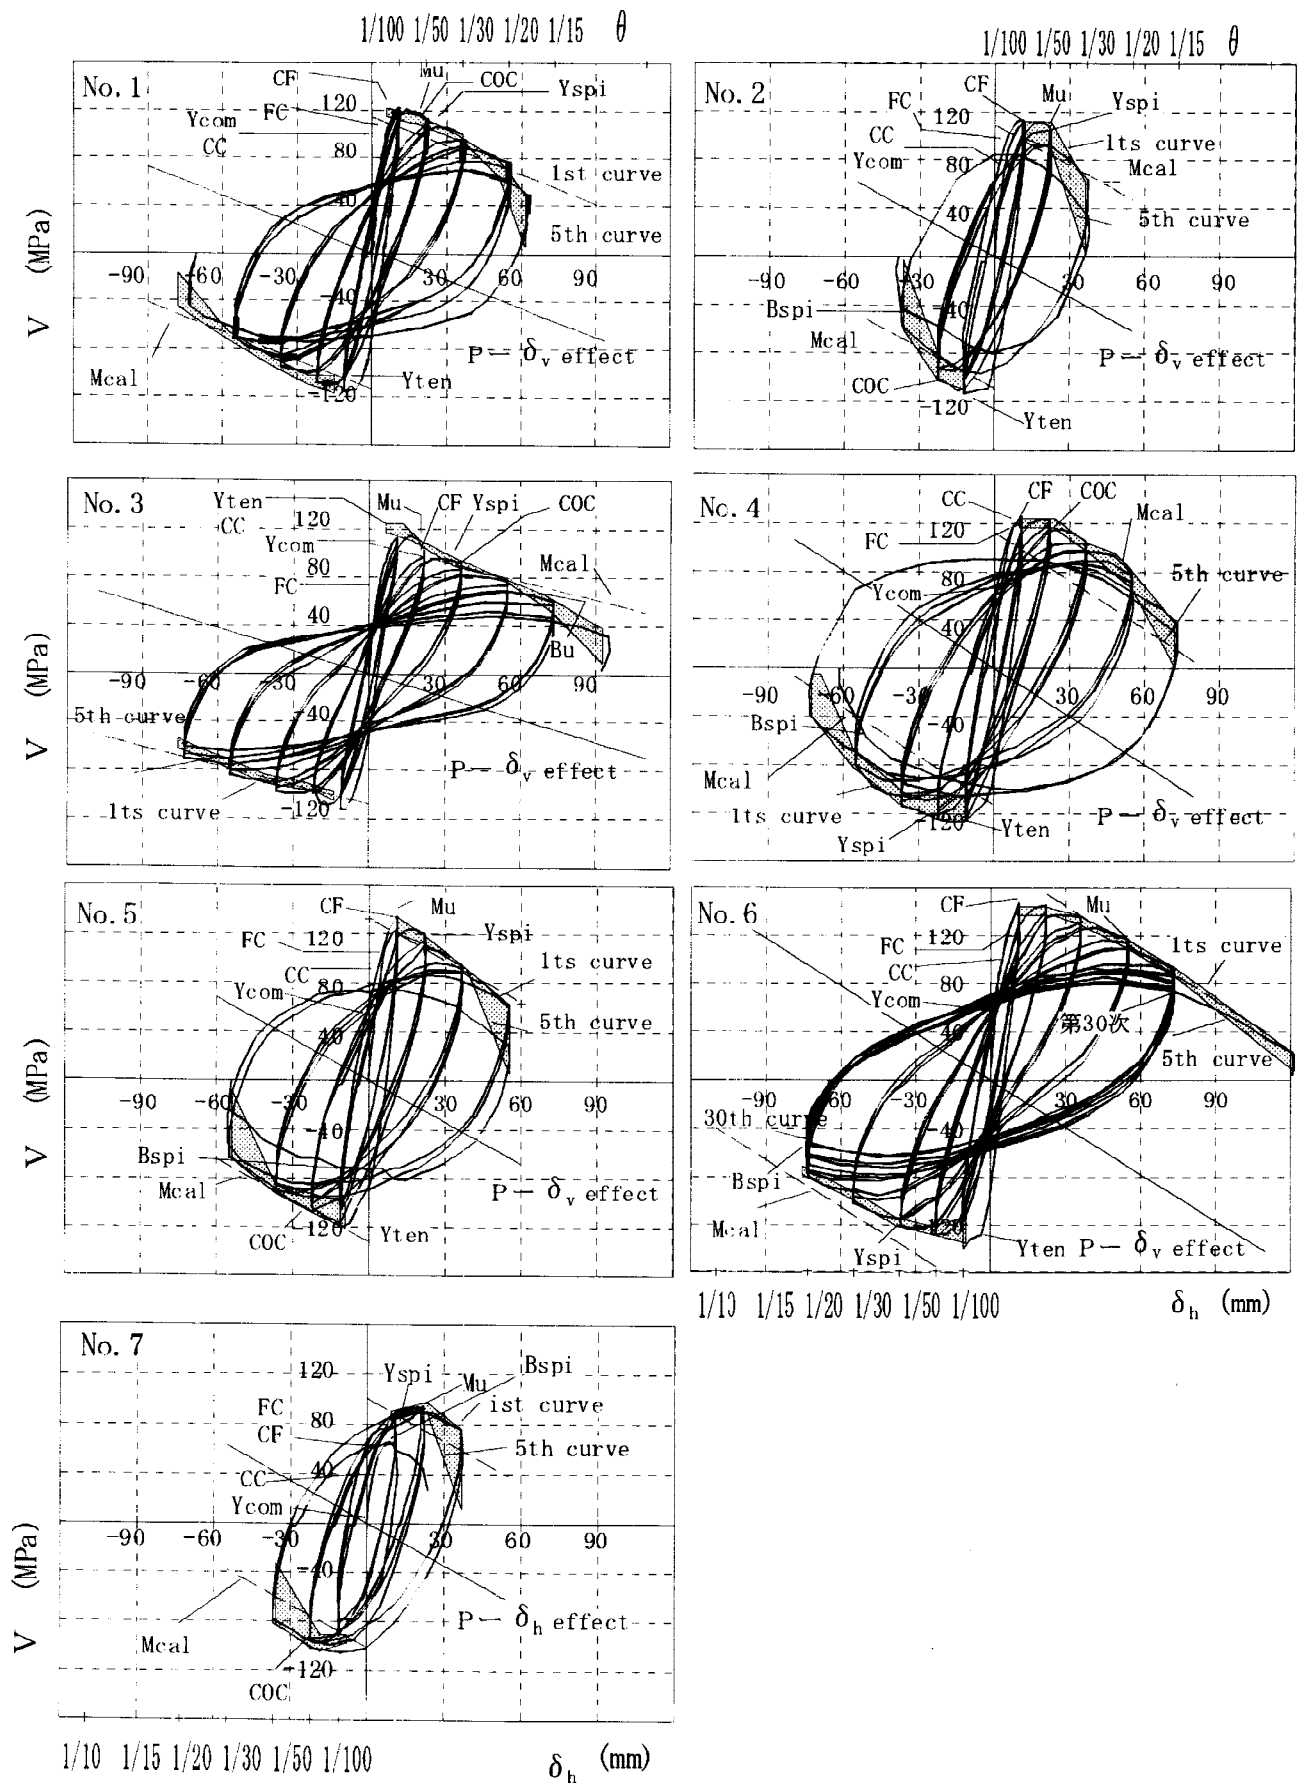


Fig. 4 Lateral load-deflection relations

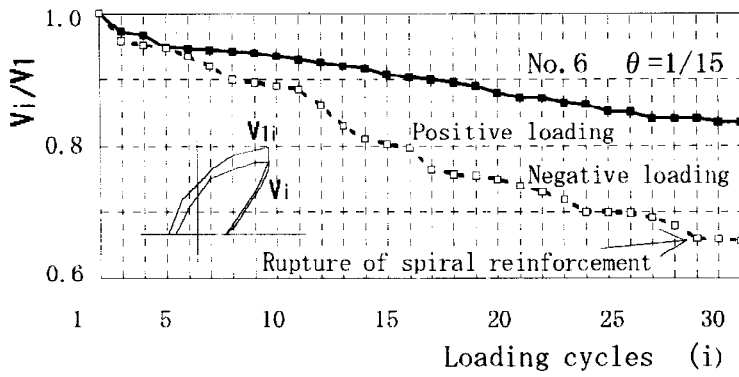


Fig. 5 Reduction ratio of load capacity of No.6 under cyclic load

of load capacity of No.6 at $\theta = 1/15$. It can be seen that the load capacity of No.6 descends greatly since the 10th cyclic loading in negative loading process, but it descends slowly and tends to converge with increase of loading cycles in positive loading process.

Specimen No.5 and No.7 were subjected to same axial load and confined with same spiral reinforcement, but they have different strength of concrete. Due to using high strength of concrete. No.5 has a smaller axial load ratio and shows larger deflection than No.7.

CHARACTERISTICS OF AXIAL COMPRESSIVE DISPLACEMENT

Figure 6 shows the results of specimens of the axial compressive displacement (δ_v)-relative lateral deflection (δ_h) of column ends. It can be seen that, with the increase of δ_h , δ_v increases, and that leads to unrecoverable axial compressive residual displacement. The residual displacement would constantly accumulate and enlarge due to the cyclic loading at each loading datum θ . These phenomena are more pronounced for the specimen with larger axial load ratio and less spiral reinforcement. Furthermore, specimens (No.1~No.5, No.7) which failure due to severe fracture and scaling of core concrete has remarkable development of δ_v in several cycles of loading just before their failure. It can be considered that a rapid increase of δ_v designates that the failure of column is upcoming.

ULTIMATE MOMENT

Table 2 shows the comparison of experimental maximum moments (M_{exp}) of specimens and calculated ones by using different methods (Suzuki et al., 1985, Suzuki et al., 1991). In the calculation of M_{cal1} and M_{cal2} , the core concrete area

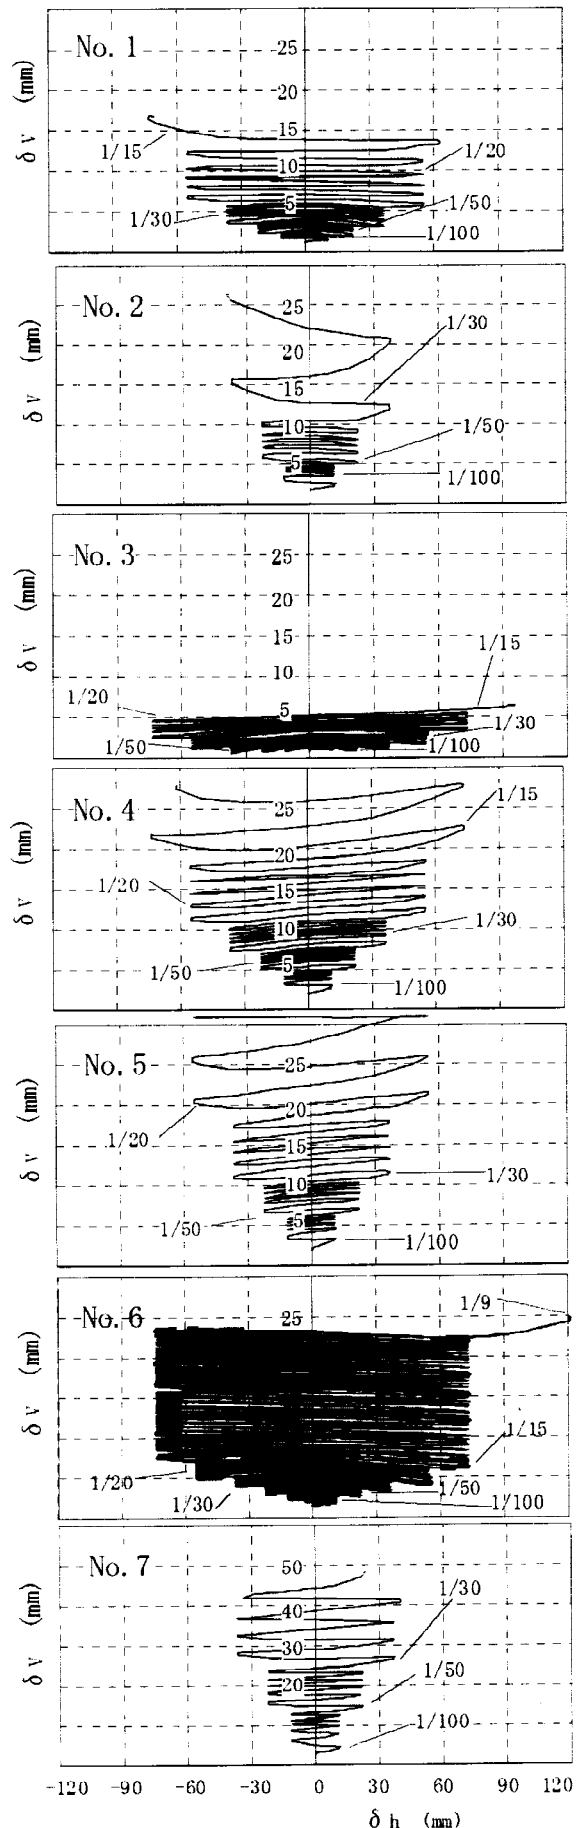


Fig. 6. Characteristics of axial compressive displacement

of calculated section is taken into consideration, according to the experimental results that cover concrete severely fractured and nearly scaled off before specimen reached its maximum moment, the compressive strength of core concrete is calculated by the strength formula (Suzuki *et al.*, 1985) of confined concrete. From Table 2 it can be seen that the ratios of M_{cal1}/M_{exp} and M_{cal2}/M_{exp} are 0.832~1.012 (averaging 0.891) and 0.754~0.993 (averaging 0.821) respectively, both are in good agreement with experimental moments.

Table 2 Comparison between experimental ultimate moments of columns and calculated ones

Specimen	M_{exp} (kN-m)	M_{cal1} (kN-m)	M_{cal2} (kN-m)	M_{cal1}/M_{exp}	M_{cal2}/M_{exp}
No.1	71.23	62.44	57.02	0.877	0.801
No.2	71.23	59.83	51.19	0.841	0.719
No.3	67.32	59.22	57.41	0.879	0.853
No.4	87.73	75.91	66.14	0.865	0.754
No.5	76.58	72.78	66.03	0.931	0.862
No.6	99.81	100.96	99.16	1.012	0.993
No.7	66.36	55.24	50.70	0.832	0.764
Average				0.891	0.821

ULTIMATE DEFLECTION CAPACITY

Figure 7 shows the ultimate relative rotation angles of columns (θ_u) versus the axial load (η) and the ratio of volume of spiral reinforcement (p_v). From Figure 8, it can be seen that the θ_u increases with increase of the p_v and decreases with increase of the η . As to circular column specimens using high-strength concrete of $f_c=50$ MPa and $f_c=30$ MPa, though subjected to high axial load with axial load ratio up to 0.6 and 1.0 respectively, they still possessed large deflection capacity of $\theta_u=1/50$, showing excellent stability, under scores of high intensity reversed cyclic lateral load when heavily confined by spiral reinforcement D6@25 and D6@15 ($p_v=2.56\%$ and $p_v=4.26\%$ respectively). Moreover, θ_u could be increased by 2~3.5 time if close spacing or high-strength spiral reinforcement be used.

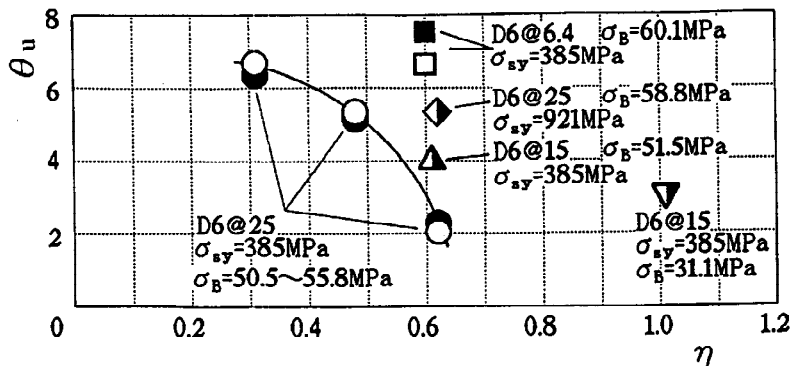


Fig. 7. Ultimate rotation angles of columns-axial load ratio and amount of circular spiral confining reinforcement

CONCLUSIONS

From the investigations presented above, the following conclusions are made.

In this experiment, the final failure of columns results from the rupture of spiral reinforcement, or the buckling of compressive longitudinal bars, or the severe fracture of core concrete (see Figure 3).

The deflection capacity of columns decreases with increase of the axial load ratio (see Figure 4 and 7).

The column, which is heavily confined by spiral reinforcement, shows excellent ductile behavior even if it is subjected high intensity reversed cyclic lateral load and constant high axial load (Figure 4, 5 and 7).

The accumulation of axial deformation of columns progresses rapidly with increase of lateral deflection and numbers of lateral loading cycles (see Figure 6).

The ultimate moments can be calculated with satisfactory by using the proposed method (see Table 2).

REFERENCES

- Suzuki, K., T. Nakatsuka and J. Cai (1985). Ductile behavior and hysteretic characteristics of partially prestressed concrete columns with circular spiral reinforcement. Technology Reports of the Osaka University, 1839,165~175.
- Suzuki, K., T. Nakatsuka and H. Nakata (1991). Design equations to estimate flexural strength of circular reinforced concrete columns. Journal of Struct. Constr. Engng, AIJ, 424, 23~34.
- Suzuki, K., T. Nakatsuka and H. Yoshida (1985). Strength and deformation characteristics of confined concrete with circular reinforcement. Journal of Material, MIJ, 376, 33~39.